



DPC: 22/30450966 DC

BSI Group Headquarters

389 Chiswick High Road London W4 4AL

Tel: +44 (0)20 8996 9000

Fax: +44 (0)20 8996 7400

www.bsigroup.com

Date: 13 October 2022

Origin: European

Latest date for receipt of comments: 06 December 2022

Project No. 2022/00114

Responsible committee: FW/0 Furniture

Interested committees:

Title: Draft BS EN 15185 Furniture - Assessment of the surface resistance to abrasion.

Please notify the secretary if you are aware of any keywords that might assist in classifying or identifying the standard or if the content of this standard

- i) has any issues related to 3rd party IPR, patent or copyright
- ii) affects other national standard(s)
- iii) requires additional national guidance or information

WARNING: THIS IS A DRAFT AND MUST NOT BE REGARDED OR USED AS A BRITISH STANDARD. THIS DRAFT IS NOT CURRENT BEYOND 06 December 2022

This draft is issued to allow comments from interested parties; all comments will be given consideration prior to publication. No acknowledgement will normally be sent. **See overleaf for information on the submission of comments.**

No copying is allowed, in any form, without prior written permission from BSI except as permitted under the Copyright, Designs and Patent Act 1988 or for circulation within a nominating organization for briefing purposes. Electronic circulation is limited to dissemination by e-mail within such an organization by committee members.

Further copies of this draft may be purchased from BSI Shop <http://shop.bsigroup.com> or from BSI Customer Services, Tel: +44(0) 20 8996 9001 or email cservices@bsigroup.com. British, International and foreign standards are also available from BSI Customer Services.

Information on the co-operating organizations represented on the committees referenced above may be obtained from <https://standardsdevelopment.bsigroup.com/>.

Responsible Committee Secretary: Miss Sarah Horsfield (BSI)

Direct tel: 020 8996 7142

E-mail: sarah.horsfield@bsigroup.com

Introduction

This draft standard is based on national and international discussions. Your comments on this draft are invited and will assist in the preparation of the consequent standard.

For international standards, comments will be reviewed by the relevant UK national committee before sending the consensus UK vote and comments to the international committee, which will then decide appropriate action. If the international standard is approved, it is usual for the text to be published as a British Standard.

For national standards, comments will be reviewed by the relevant UK national committee and the resulting standards published as a British Standard.

UK Vote

Please indicate whether you consider the UK should submit a negative (with supporting technical reasons) or positive vote on this draft. Please indicate if you are aware of any reason why this draft standard should not be published as a British Standard.

Submission of Comments

- **Annotated drafts are not acceptable and will be rejected.**
- All comments should be submitted online at <https://standardsdevelopment.bsigroup.com/>. You will need to register in order to comment.

Template for comments and secretariat observations

Date: xx/xx/20xx	Document: ISO/DIS xxxx
------------------	------------------------

1	2	(3)	4	5	(6)	7
MB	Clause No./ Subclause No./Annex (e.g. 3.1)	Paragraph/ Figure/Table/Note	Type of comment	Comment (justification for change) by the MB	Proposed change by the MB	Secretariat observations on each comment submitted
	3.1	Definition 1	ed	Definition is ambiguous and needs clarifying.	Amend to read '...so that the mains connector to which no connection...'	
	6.4	Paragraph 2	te	The use of the UV photometer as an alternative cannot be supported as serious problems have been encountered in its use in the UK.	Delete reference to UV photometer.	

English Version

Furniture - Assessment of the surface resistance to abrasion

Ameublement - Évaluation de la résistance de la surface à l'abrasion

Möbel - Bewertung der Abriebfestigkeit von Oberflächen

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 207.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents	Page
European foreword	3
1 Scope.....	4
2 Normative references.....	4
3 Terms and definitions	4
4 Principle	5
5 Apparatus and materials.....	5
5.1 Cleaning cloth	5
5.2 Calibration plates.....	5
5.3 Abrasion paper strips.....	5
5.4 Test apparatus	5
5.5 Balance	6
5.6 Conditioning chamber.....	6
5.7 Diffuse light source.....	6
6 Preparation and conditioning.....	6
6.1 Conditioning	6
6.2 Test surface.....	6
6.3 Preparation of test surfaces and abrasive paper	6
Figure 1 — Test surface area divided into four quadrants	7
7 Test procedure.....	7
7.1 Preparation of abrasive wheels.....	7
7.2 Calibration of abrasive paper.....	7
7.3 Abrasion of test area.....	7
7.4 Determination of initial wear point (IP)	8
7.4.1 General.....	8
7.4.2 Foil, uncoated and coated laminate and melamine faced boards	8
7.4.3 Pigmented lacquers	8
7.4.4 Transparent lacquers on wood or lignocellulosic-substrates.....	8
8 Assessment of results.....	9
9 Test report.....	9
Annex A (informative) Calibration and maintenance of Taber abrasion equipment	10
Annex B (normative) Examples of abrasion traces	14
Bibliography	16

European foreword

This document (prEN 15185:2022) has been prepared by Technical Committee CEN/TC 207 “Furniture”, the secretariat of which is held by UNI.

This document is currently submitted to the CEN Enquiry.

This document will supersede EN 15185:2011.

Compared with EN 15185:2011, the following modifications have been made:

- a) deviations of 5.4 “Test apparatus” modified and additional bullet regarding table rotary speed added;
- b) revision of 7.2 “Calibration of abrasive paper” and formula added for calculating a correction factor;
- c) revision of title 7.4.2 to “Foil, uncoated and coated laminate and melamine faced boards”;
- d) revision of title 7.4.4 to “Transparent lacquers on wood or lignocellulosic-substrates” and modified IP;
- e) completion of the statement on A.3.4 “Alignment - Dual head abrader”;
- f) Annex C deleted
- g) the significant changes in the revised edition are now given in the European foreword;
- h) Bibliography updated;
- i) document editorially revised in its entirety.

1 Scope

This document specifies a method for the assessment of the abrasion resistance of surfaces with foils, laminates, melamine faced boards, pigmented and transparent lacquers.

It does not apply to leather and textile surfaces.

It does not apply to the surfaces covered by EN 14434.

The test is intended to be carried out on an unused part of the finished furniture, but can be carried out on test panels of the same material, finished in an identical manner to the finished product, and of a size sufficient to meet the requirements of the test.

The test is intended to be carried out on unused surfaces.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 6506-1, *Metallic materials - Brinell hardness test - Part 1: Test method (ISO 6506-1)*

ISO 9352, *Plastics — Determination of resistance to wear by abrasive wheels*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

test surface

part of the test panel

3.2

test panel

panel including the test surface

Note 1 to entry: It may be cut from a finished item of furniture or it may be a separate panel produced in the same manner as the finished item of furniture.

3.3

test area

part of the test surface under the wheels covered by the abrasion paper strips (5.3)

3.4

colour rendering index

R_a

unitless number that specifies how well the colour of an object appears under illumination by a light source compared to a reference light source

4 Principle

The test simulates the ability of the furniture surface under test, to resist abrasive wear-through. Abrasion is achieved by rotating a specimen in contact with a pair of loaded cylindrical wheels covered with abrasive paper. The wheels are positioned so that their cylindrical faces are equidistant from the specimen's axis of rotation but not tangential to it. As they are turned by the rotating specimen they abrade an annular track on the specimen's surface. The number of revolutions of the specimen required to cause one defined degree of abrasion, is used as measurement of resistance to surface wear.

5 Apparatus and materials

5.1 Cleaning cloth

White soft absorbent cloth.

5.2 Calibration plates

Taber S-34 ¹ or equivalent, having a thickness of $(0,8 \pm 0,1)$ mm and a Brinell hardness of (48 ± 2) when tested in accordance with EN ISO 6506-1, except that the ball diameter shall be 5 mm and the load 360 N.

5.3 Abrasion paper strips

Taber S-42 ² or equivalent, of width $(12,7 \pm 0,1)$ mm and length about 160 mm, according to the following specifications:

- a) paper of grammage from 70 g/m² to 100 g/m²;
- b) open coated 180 grit powdered aluminium oxide (Al₂O₃) having a particle size such that it will pass through a sieve of aperture 100 µm and remain on a sieve having an aperture of 63 µm;
- c) adhesive backing.

5.4 Test apparatus

As specified in ISO 9352 with following deviations ³:

- a) the hardness of wheels' rubber layer shall be between 60 Shore A and 70 Shore A, when measured in the middle of the contact surface; make 4 measurements and calculate the average value;

The laboratories should measure the hardness at least once every 12 months. Checking of rubber wheels geometry shall be performed. If any deformation is observed the rubber wheel should be rejected.

- b) weight of loading: every wheel shall apply a force $(5,4 \pm 0,2)$ N on the sample;
- c) vacuum system: the suction nozzle should be as close to the surface as possible without rubbing it. The vacuum system shall remove practically all the dust;

¹ Taber S-34 is an example of a suitable product available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by CEN of this product.

² Taber S-42 is an example of a suitable product available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by CEN of this product.

³ A suitable machine is available from Taber Acquisition Corp., Taber industries, 455 Bryant St P.O. Box 164, North Tonawanda, NY 14120, USA. This information is given for the convenience of users of this document and does not constitute an endorsement by CEN of the machine.

- d) the distance between the middle axis of the sample holder and the wheels should be calibrated according to Annex A;
- e) the table rotary speed shall be (60 ± 2) r/min.

5.5 Balance

The accuracy of the balance shall be 1 mg.

5.6 Conditioning chamber

A chamber with a standard atmosphere of (23 ± 2) °C, relative humidity (50 ± 5) %.

5.7 Diffuse light source

Light source providing evenly diffused light giving an illumination on the test surface of $(1\,200 \pm 400)$ lx. This may either be diffused daylight or be diffused artificial daylight.

The daylight should be unaffected by surrounding trees, buildings, etc. When artificial light is used it is recommended that it should have a correlated colour temperature of $(6\,500 \pm 50)$ K and a colour rendering index (R_a) greater than 92, by using a colour matching booth in accordance with EN ISO 3668.

6 Preparation and conditioning

6.1 Conditioning

Conditioning of test surface shall begin at least one week before testing and shall be carried out in air at a temperature of (23 ± 2) °C and relative humidity of (50 ± 5) %.

NOTE The final curing of some coatings, such as waterborne coatings, can require a longer conditioning time.

The conditioning time shall be stated in the test report.

Condition the abrasion paper strips at least for one week in the conditioning atmosphere of (23 ± 2) °C and (50 ± 5) % RH, before testing; see 5.6.

6.2 Test surface

Three test surfaces shall be prepared.

The test surface shall be taken at least 5 mm from the edge of the test panel.

Each test surface shall be a piece of test panel, shaped to fit the type of clamping device used. It shall usually be a square of 100 mm × 100 mm, and including an appropriated hole drilled in the centre to place the test surface in the axis of the apparatus.

The test surface shall be carefully wiped with a cleaning cloth (5.1) before the test.

The test surface shall be substantially flat, and free from defect such as scratch, colour fading and surface folding.

6.3 Preparation of test surfaces and abrasive paper

Using a suitable marker pen, mark the surface of each test surface with two lines at right angles, diagonals, so that the surface area is divided into four quadrants, according to Figure 1.

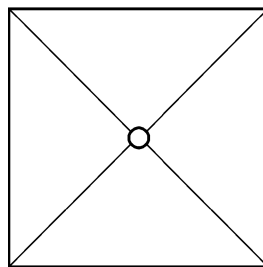


Figure 1 — Test surface area divided into four quadrants

7 Test procedure

7.1 Preparation of abrasive wheels

Bond a strip of conditioned unused abrasive paper to each of the rubber covered wheels. Ensure that the cylindrical surface is completely covered, but without any overlapping of the abrasive paper.

7.2 Calibration of abrasive paper

Carry out this calibration three times for each box.

Prepare two abrasive wheels, in the correct hardness range (5.4), with conditioned unused strips of abrasive paper.

Clamp a zinc plate in the specimen holder, start the vacuum device, set the revolution-counter to zero, lower the wheels, ensuring that the arms are horizontal and the load on the zinc plate is $(5,4 \pm 0,2)$ N, and abrade the zinc plate for 500 revolutions. Wipe the zinc plate clean and weigh to the nearest 1 mg. Replace the abrasive paper on the wheels with preconditioned unused strips from the same batch, clamp the same zinc plate in the specimen holder, lower the abrasive wheels and operate the suction device. Abrade the zinc plate for an additional 500 revolutions, then wipe it clean and reweigh it to the nearest 1 mg.

Any box containing abrasive paper which causes a loss in mass of the zinc plate which is outside (110 ± 20) mg, for any pair of calibrate strips, shall not be used for testing.

Calculate a correction factor by use of Formula (1):

$$CF = \frac{(avg)}{(110)} \quad (1)$$

where

CF is the correction factor;

avg is the mean value if three calibrations, in mg;

110 is the limit for the mass loss value of the zinc plate, in mg.

Report this factor in the test report.

7.3 Abrasion of test area

Perform the test immediately after removal of the test surface and calibrated abrasive paper from the conditioning atmosphere.

Prepare two wheels, in the correct hardness range, with preconditioned unused abrasive paper from the same box previously approved by calibration. Fit the wheels to the machine and set the revolution counter to zero.

Clamp the test surface in the holder, ensuring that it is placed horizontally. Lower the abrasive wheels on to the specimen, ensuring that the arms are horizontal and the load on the samples is $(5,4 \pm 0,2)$ N. Start the vacuum device for removing practically all the dust, and begin abrading the test area.

NOTE If the arms are not horizontal, then there are two possibilities: to modify appropriately the apparatus or to reduce appropriately the thickness of the test surface before the conditioning; see Clause 6.

Before each assessment, in order to correctly assess the Initial Wear Point (IP); see 7.4, ensure the surface is free of dust. If needed, wipe with the cleaning cloth.

At the beginning of the test, the visual assessment shall be carried out, depending on the expected IP (see 7.4), as follows:

- under 200 revolutions, every 10 cycles;
- over 200 revolutions, every 25 cycles;
- over 500 revolutions, every 50 cycles;
- when close to IP, the assessment shall be carried out every 10 cycles.

Replace the abrasive paper after every 200 revolutions.

Continue the test in this way until the IP is reached. Record the number of revolutions.

7.4 Determination of initial wear point (IP)

7.4.1 General

The determination of IP shall be established by one observer experienced in this type of assessment. In case of a dispute, three observers shall carry out the visual assessment.

The determination of IP shall be carried out under the light described above; see 5.7.

To assess the IP, use the following.

7.4.2 Foil, uncoated and coated laminate and melamine faced boards

The first clearly recognizable wear-through of the print, pattern or plain colour appears and the sublayer becomes exposed in four quadrants.

Compare the examined test surface with the examples for IP points; see Table B.1.

The sub-layer for printed patterns is the background on which the pattern is printed; for plain colours it is the first sub-layer of different colour.

7.4.3 Pigmented lacquers

The first clearly recognizable wear-through of the substrate, or layer with other colour, appears in all the four quadrants.

7.4.4 Transparent lacquers on wood or lignocellulosic-substrates

The first clearly recognizable wear-through of the lacquers becomes exposed in four quadrants; see examples in Table B.2.

The following procedure shall be used:

- draw a circle on the abrasion trace by using a marker pen giving a contrast with the sample colour (not waterproof ink);
- if the ink penetrates into the wood grain along the grain direction in any part of abrasion trace, the IP point is nearly reached;
- the IP shall be assessed by using any agent suitable for marking when the wood or wood veneer substrate is exposed, such as a water solution of 0,1 % (m/m) methyl blue. The liquid shall be spread over the surface and removed with a dry paper in order to colour the abraded surface and distinguish it from the not completely abraded surface.

Compare the examined test surface with the examples for IP points and deviations described in Annex B.

8 Assessment of results

The abrasion resistance of the test surface shall be expressed as the number of revolutions at which IP is reached.

The test result shall be the mean value of the 3 test surfaces rounded to the nearest 10 cycles.

9 Test report

The test report shall include at least the following information:

- a) reference to this document;
- b) the name, type and if the test surface has been cut in order to get the horizontality of the arms;
- c) conditioning time;
- d) the mean abrasion resistance for the sample under test, in revolutions;
- e) the correction factor;
- f) any deviations from this document;
- g) the name and address of the test facility;
- h) the date of the test.

Annex A (informative)

Calibration and maintenance of Taber abrasion equipment

A.1 General

Calibration and maintenance of the equipment shall be carried out, in order to ensure correct and comparable test results.

The procedures contained in this annex have been developed for the Taber equipment. The principles may, however, be applied to similar equipment.

Three parts have been identified as potential sources of error. Each is addressed separately in this annex; however, each is dependent upon the other. The first source of error is bearing wear, the second is shaft wear and the third is alignment of the arms.

Improper alignment of the abrasive wheels can lead to each wheel abrading a different path from the wheel across the sample as well as the wheels on other machines. The path surface area can differ by as much as 20 % and the area abraded by both wheels on a sample could be less than 50 % of the total abraded area for that sample.

The procedures outlined below do not necessarily address all potential sources of variance.

A.2 Apparatus

A.2.1 Calibration block

Calibration block of preferably steel measuring:

— $(77,90 \pm 0,02) \text{ mm} \times (77,90 \pm 0,02) \text{ mm} \times (25,00 \pm 0,02) \text{ mm}$

with a hole drilled and threaded with UNF 1/4 inch in accordance with EN/ISO/ANSI in the centre $(38,95 \pm 0,02) \text{ mm}$ of the $(77,90 \pm 0,02) \text{ mm} \times (77,90 \pm 0,02) \text{ mm}$ face such that the block can be threaded onto the holder disc of the abrader. All edges shall be made with a radius of 1 mm.

A.2.2 Feeler gauges

Feeler gauges of various thickness.

A.2.3 Shim washers

Shim washers of various thickness ranging from 0,05 mm and up. The inside diameter shall be 8 mm and the outside diameter shall be 13 mm.

A.3 Procedure

A.3.1 Bearing wear

Examine each arm of the abrader visually and by hand for any bearing wear. Specific areas to examine are the pivot areas of the abrader arm and the shaft on which the wheel revolve. This includes, but is not limited to, any sideways, twisting, or other motion outside the specific rotation of the arm or the shaft. Any movement noted, other than the pivoting of the arm or shaft, requires that further examination be made to determine the cause of the excess movement.

Specific repairs shall be completed before attempting subsequent portions of the procedure.

A.3.2 Shaft wear

In certain instances, the shaft for the abrader wheel may slide end to end. This movement shall be eliminated by placing shim washers of appropriate thickness between the bearing face and the shaft keeper ring on the end of the shaft opposite the abrader wheel mounting. This can be measured using the feeler gauges to measure the gap prior to disassembly and the appropriate thickness of shim washers placed on the shaft.

A.3.3 Alignment

Remove the rubber wheels from their respective shaft mounting and set aside. Remove the rubber mat on the sample table (if used).

Attach the calibration block to the table by the threaded mount (see Figure A.1).

Gently lower the arms with the exposed shaft ends onto the block. Rotate the block to square the block with the shaft face of each arm. The face of each shaft shall squarely meet the adjacent face of the calibration block without force and without any gap. If the arm does not seat squarely onto the block or leaves a gap between the face and block, then that arm shall be aligned.

If the alignment does not allow the wheel shaft to rest against the shaft hub and face, the arm shall be moved away from the block by loosening the two set screws on the top of the machine toward the back that holds the shaft on which the arm pivots and moving the entire arm assembly away from the block enough so that the shaft face and hub rest squarely against the calibration block. Retighten the set screws and recheck.

If the alignment leaves a gap between the shaft hub/face and the calibration block, the arm shall be moved toward the block by loosening the two set screws on the top of the machine toward the back that holds the shaft on which the arm pivots and moving the entire arm assembly towards the block enough so that the shaft face and hub rest squarely against the calibration block. Retighten the set screws and recheck.

A.3.4 Alignment - Dual head abrader

In the case of a dual head abrader, the alignment is more complex due to the common mount utilized by the shaft holding the interior arms for each side of the abrader. In the case of a dual head abrader, the following order of alignment adjustments is made.

Remove rubber wheels and table mats from both heads and attach the calibration block to the left head.

Check Arm 1 for correct alignment (see Figure A.2). If adjustment is required, loosen SS1 and SS2 and move the arm assembly in or out to squarely align the shaft face/hub to the calibration block. Retighten the set screws and recheck.


Check Arm 2 for correct alignment. If adjustment is required, loosen SS3, SS4 and SS5 and move the arm assembly in or out to squarely align the shaft face/hub to the calibration block. Retighten the set screws SS3 and SS4 and recheck.

Remove the calibration block from the left head and attach it to the right head.

Check Arm 3 for correct alignment. SS5 is loose. Seat the shaft beneath SS5 fully to the left and check the Arm 3 alignment. If the shaft face/hub is too tight to the calibration block, shims shall be removed from Arm 3 assembly at the point the shaft seats into the arm at Point X. Part the assembly by moving the Arm 3 and shaft under SS5 fully to the right and remove the shims as needed to squarely place the shaft face/hub against the calibration block. Retighten the set screw SS5 and recheck. If the shaft face/hub is loose against the calibration block, shims shall be added to the arm 3 at the point the shafts seats into the arm at point X. Measure the gap between the block and the shaft face/hub with the feeler gauge to determine the thickness of shim washers to add. Part the assembly by moving the Arm 3 and shaft under

SS5 fully to the right and add the shims as needed to squarely place the shaft face/hub against the calibration block. Retighten the set screw SS5 and recheck.

Check Arm 4 for correct alignment. If adjustment is required, loosen SS6 and SS7 and move the arm assembly in or out to squarely align the shaft face/hub to the calibration block. Retighten the set screws and recheck for correct alignment.

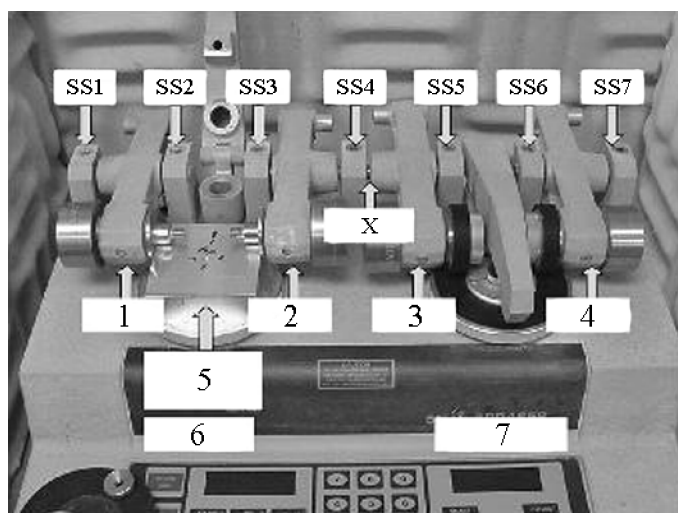


Key

- 1 arm 1
- 2 arm 2
- 3 arm 3
- 4 arm 4
- 5 calibration block
- 6 left head
- 7 right head

Figure A.1 — Dual head abrader with calibration block and identification points

Dimensions in millimetres

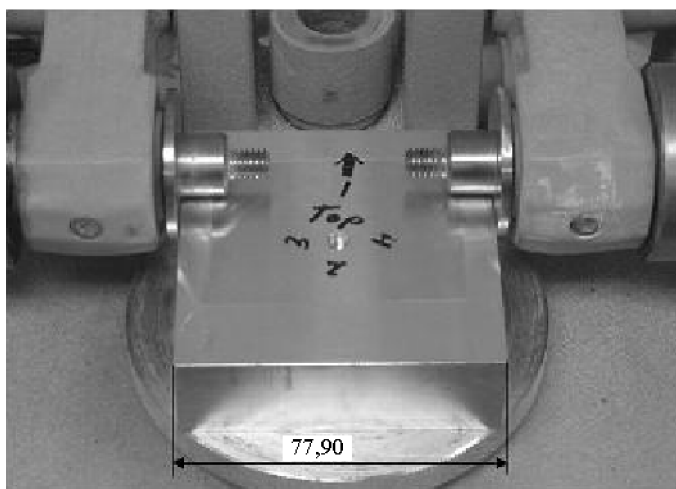**Figure A.2 — Calibration block with arms correctly aligned**

Annex B (normative)

Examples of abrasion traces

Table B.1 — Examples of abrasion traces

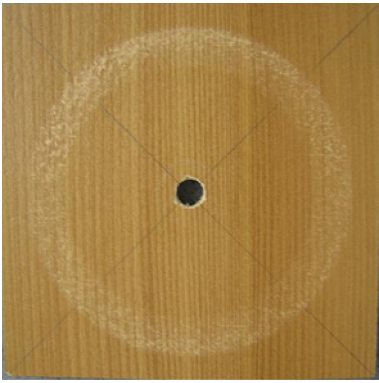
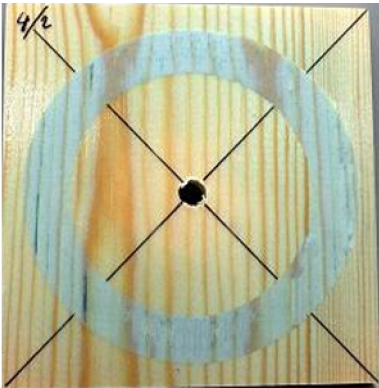
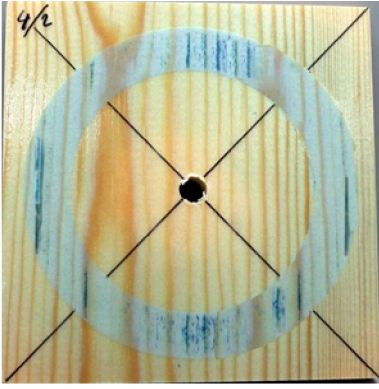
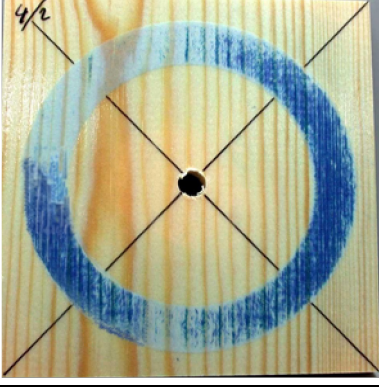
Description	Example of abrasion traces on printings
IP is not reached (no abrasion until the print in all 4 quadrants)	
IP is correct (beginning abrasion until the print in all 4 quadrants)	
IP is passed (too many revolutions after abrasion until the substrate)	

Table B.2 — Examples of abrasion traces on lacquers

Description	Example of abrasion traces on lacquers
IP is not reached (no abrasion until the wood surface in all 4 quadrants)	
IP is correct (beginning abrasion until the wood surface in all 4 quadrants)	
IP is passed (too many revolutions after abrasion until the substrate)	

Bibliography

- [1] EN ISO 3668, *Paints and varnishes - Visual comparison of colour of paints (ISO 3668:2017)*
- [2] EN 14434, *Writing boards for educational institutions - Ergonomic, technical and safety requirements and their test methods*